



УДК 541.64: 544.725

# Hydration of heterogeneous cation-exchange membranes in hydrogen and amino acids forms. I. Study by IR-spectroscopy

Lantsuzskaya E.V., Eliseeva T.V., Oros G.Yu.,  
Semenov V.F., Chernikov M.A., Sholokhova A.Yu.

*Voronezh State University, Voronezh*

Received 22.12.2013

## Abstract

Hydration characteristics of heterogeneous sulfocation-exchange membranes МК-40 and FTСМ-Е in hydrogen and amino acid's forms are studied by IR-spectroscopy. Energy of hydrogen bonds in ion-exchange membrane is calculated on the basis of absorption strips displacement in the IR-spectrum. Basic amino acids sorption by the membrane leads to a decrease of total water content in the membrane phase and to an increase of water molecules fraction having high values of hydrogen bonds energy.

**Keywords:** arginine, histidine, cation-exchange membrane, hydration, IR-spectrum.

Гидратационные характеристики гетерогенных сульфокатионообменных мембран МК-40 и FTСМ-Е в водородной и аминокислотных формах изучены методом ИК-спектроскопии. Энергия водородных связей в ионообменной мембране рассчитана на основе сдвига полос поглощения в ИК-спектре. Сорбция мембраной основных аминокислот приводит к снижению общего содержания воды в фазе мембраны и к увеличению доли молекул воды с высокой энергией водородных связей.

**Ключевые слова:** аргинин, гистидин, катионообменная мембрана, гидратация, ИК-спектр

## Introduction

Studies of the ion-exchange membranes hydration are an important stage in an analysis of transfer processes in biological and synthetic membranes. They allow refining theoretical concepts of the nature and mechanism of amino acids transport. Thus, such studies are necessary for the development of methods for the isolation and demineralization of substances by membrane methods [1]. The present work deals with amino acid forms of sulfocation-exchange membranes.

Ion-exchange membranes perform only in aqueous media, and irreversibly change their initial separation and structural properties after dehydration. The content and state of water in ion-exchange membranes substantially influence their physicochemical properties and transport characteristics [2-3]. The nature of the polymeric matrix and the type of functional groups and counterions determine the membranes hydration. Close interrelation between the structure and properties of water and membranes determines the importance of studies of the hydration characteristics of ion-exchange membranes. The purpose of this

work is to estimate the hydration of heterogeneous cation-exchange membranes in the arginine, histidine and  $H^+$ -forms.

## Experimental

The objects of this study are arginine, histidine and heterogeneous sulfopolyesterene cation-exchange membranes: MK-40 (produced by “Shchekinoazot”, Russia), FTCEM-E (produced by FuMa-Tech, Germany).

The membranes were prepared according to GOST State Standard 17553-72 and converted into the target form according to the technique described in [4].

The solutions of amino acids (produced by Ajinomoto) are analyzed by the method of photometry based on copper complexes formation [5]. Water sorption is determined by gravimetric method according to GOST 17554-72 [4]. IR-spectra of membrane samples are obtained using Vertex-70 Bruker FTIR-spectrometer in the region  $4000-500\text{ cm}^{-1}$ .

## Results and discussion

The nature of the polymeric backbone and the type of functional groups and counterions in turn determine the hydration of membranes [6]. In this study the hydration of heterogeneous cation-exchange membranes in arginine, histidine and  $H^+$ - forms is estimated.

The studied membranes have identical functional groups, however, distinction in the nature and structure of polymer matrix has an influence on the state and quantity of water in membrane phase and, as consequence, on electro dialysis concentration parameters [7]. The hydration of cation-exchange membranes after sorption of basic amino acid is estimated by the gravimetric method. The water content in MK-40 and FTCEM-E cation-exchange membranes in arginine and  $H^+$ -forms is shown in Table 1. The presence of amino acid's bipolar ions limits the sorption of water and changes the amount and state of water in the membrane phase. It follows from our data that saturation of ion-exchange membranes with arginine or histidine causes decrease of water uptake [8].

Table 1. Water content for MK-40 and FTCEM-E cation-exchange membranes in arginine, histidine and  $H^+$ -forms

The membrane	Membrane form	Water content, %	Specific water capacity, mol $H_2O/SO_3^-$
MK-40	$H^+$	56.7	12.6
	Arg	36.2	8.0
	His	41.2	9.1
FTCEM-E	$H^+$	39.3	11.5
	Arg	25.6	7.5
	His	28.1	8.2

Water content for two membranes (in mass. percentage) differs significantly, but specific water capacity is similar. This is due to the fact that MK-40 membrane has higher value of total exchange capacity (that means - more sulfo-groups) of 2.5 mmol/g of absolutely dry membrane, than FTCEM-E membrane, which capacity is equal to 1.9 mol/g.

Hydration of heterogeneous MK-40 sulfocation-exchange membranes in  $H^+$ , arginine and histidine forms is studied by IR-spectroscopy method. The energy of

hydrogen bonds between water molecules in ion-exchange membranes is calculated on the basis of bands frequency shift in the IR-spectrum. The existence of structure and energy heterogeneity of water associates in studied membranes is shown.

Vibrational spectra make it possible not only to reveal the bands of absorption corresponding to matrix, functional groups and counter-ions of membrane but also to establish the existence and force of hydrogen bonding. Deformation vibrations of water molecules appear at 1600-1750  $\text{cm}^{-1}$  and stretching vibrations of  $-\text{O}-\text{H}$  bonds – at 3000-4000  $\text{cm}^{-1}$ . Appearance of distortions in IR-spectrum (shift of frequency and broadening of spectral band, intensity change) accompanying hydrogen bonds formation can be a criterion of their formation and enables to estimate the energy of bonding.

For the assessment of hydration properties of membrane gel phase one can use the bands of stretching vibrations of OH-groups at the region 3700-3000  $\text{cm}^{-1}$  which are the most sensitive to hydrogen bonds modification. Fig.1 shows IR-spectra of MK-40 membrane in arginine, histidine and  $\text{H}^+$ -forms.

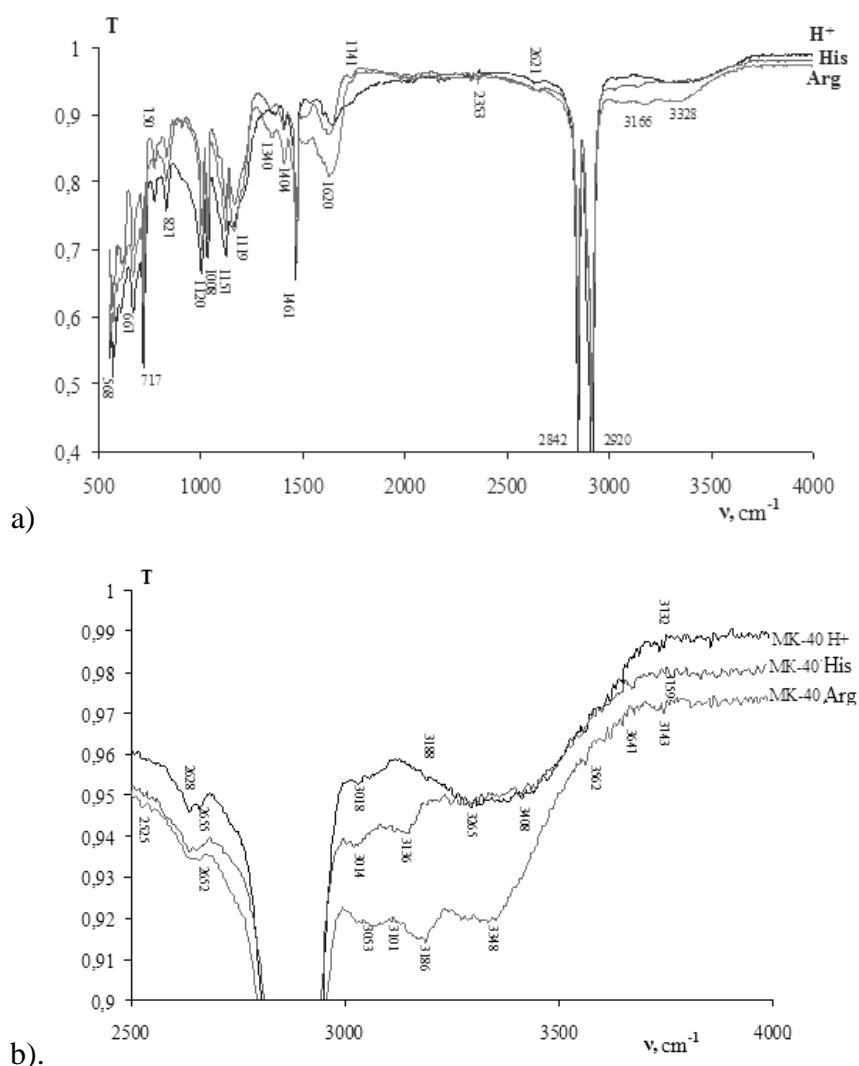


Fig. 1. IR-spectra of membrane MK-40 in arginine, histidine and  $\text{H}^+$ -forms.  
a) 500-4000  $\text{cm}^{-1}$ , b) 2500-4000  $\text{cm}^{-1}$

The dominant minima of transmission in the spectra of MK-40 membrane are minima at 2920, 2842  $\text{cm}^{-1}$ , corresponding to asymmetric and symmetric vibrations of  $-\text{CH}$  and  $-\text{CH}_2$  groups. Minima at 1008, 1120, 1157  $\text{cm}^{-1}$  deal with stretching vibrations of  $-\text{SO}_3$  groups, minima at 1472, 1462  $\text{cm}^{-1}$  correspond to deformation vibrations of  $\text{CH}$  и  $\text{CH}_2$

groups. Peaks at 773 and 831  $\text{cm}^{-1}$  confirm the appearance of not flat deformation vibrations of -CH in substituted benzene ring [9].

The vibrations of C-S bond of sulfo-group connected with benzene ring are confirmed by the minima at 750 и 721  $\text{cm}^{-1}$ . The deformation vibrations of C-H of benzene ring one can observe at 667  $\text{cm}^{-1}$ .

IR-spectra of the membrane in histidine and arginine forms contain band at 1620  $\text{cm}^{-1}$  – deformation vibrations of  $\text{NH}_3^+$  (I amino acid band) [9]. Also it is possible to reveal the appearance of the minimum at 1340  $\text{cm}^{-1}$  – symmetric vibrations of  $-\text{COO}^-$  groups.

In IR-spectrum of MK-40 for the region 3000-4000  $\text{cm}^{-1}$  shoulder is found at 3686  $\text{cm}^{-1}$  (it shifts to 3560  $\text{cm}^{-1}$  for amino acid form indicating the formation of more strong associates) and the wide band including several peaks is situated in the region 3470-3250  $\text{cm}^{-1}$ . According to G. Zundel [10-11] a continuous absorption in this region appears in the case of existence of two water molecules per one proton, i.e. in the case of  $\text{H}_5\text{O}_2^+$  formation. It can be confirmed by the appearance of the band at 1740  $\text{cm}^{-1}$ . For the membrane in arginine form one can observe also bands corresponding to the stretching vibrations of guanidinium fragment and amino group: 3333, 3285, 3173  $\text{cm}^{-1}$ .

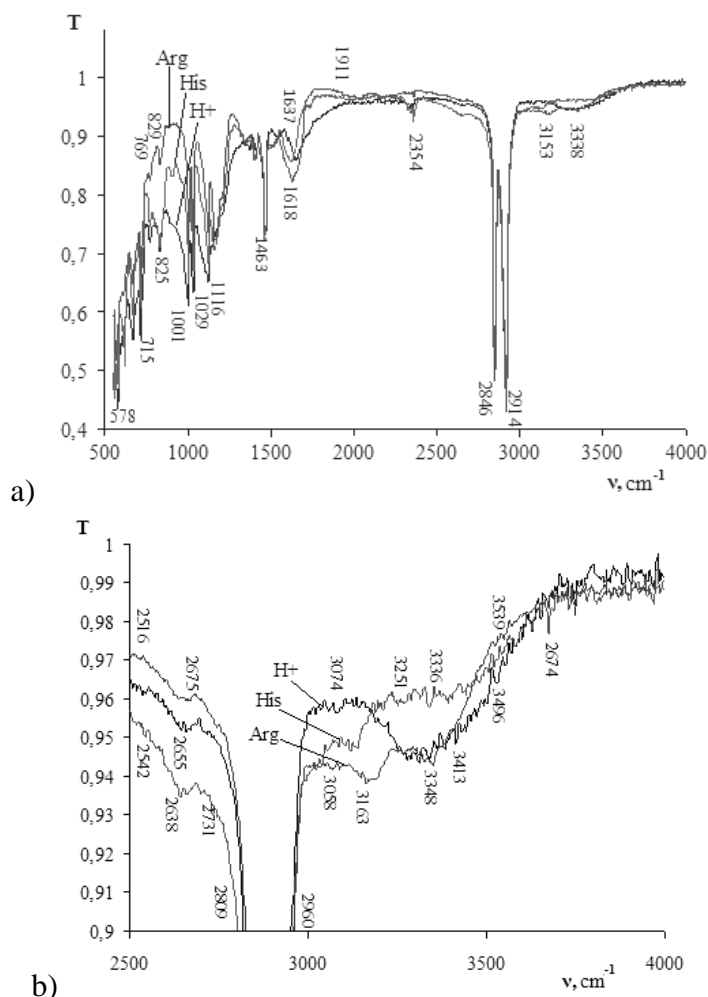


Fig. 2. IR-spectra of FTCEM-E membrane in arginine, histidine and  $\text{H}^+$ -forms.

a) 500-4000  $\text{cm}^{-1}$ , b) 2500-4000  $\text{cm}^{-1}$

Fig. 2 shows IR-spectra of FTCEM-E membrane in arginine, histidine and  $\text{H}^+$ -forms. The spectrum region 2500-4000  $\text{cm}^{-1}$  is presented separately in fig. 2b.

From the IR-spectra analysis we conclude that FTCEM-E membrane contains sulfo-groups as functional groups, minima at 1001, 1006, 1033, 1463  $\text{cm}^{-1}$  deal with stretching vibrations of  $-\text{SO}_3$  groups. Several bands characterize the polymer matrix of the membrane. In the spectra of FTCEM-E membrane very strong minima at 2914, 2846  $\text{cm}^{-1}$ , corresponding to asymmetric and symmetric vibrations of  $-\text{CH}$  and  $-\text{CH}_2$  groups are observed. Peaks at 769 and 835  $\text{cm}^{-1}$  confirm the appearance of not flat deformation vibrations of  $-\text{CH}$  in substituted benzene ring. The bands listed above are observed in the spectra of both hydrogen and arginine forms.

IR-spectrum of the membrane in histidine form contains band at 1637  $\text{cm}^{-1}$  – deformation vibrations of  $\text{NH}_3^+$  (I amino acid band), the arginine form demonstrates I amino acid band at 1618  $\text{cm}^{-1}$  [9]. Also it is possible to reveal the appearance of the minimum at 1722  $\text{cm}^{-1}$  – symmetric vibrations of  $-\text{COO}^-$  groups.

Note that the intensity in the region 3500-3200  $\text{cm}^{-1}$  in histidine form is smaller than in hydrogen form, in the region 3000 -3200 $\text{cm}^{-1}$  on the contrary the bands intensity in histidine form is larger. So, number of strongly bounded water in the amino acid form of membrane rises and the amount of weak bounded water decreases. For the membrane in histidine form one can observe also band corresponding to the vibrations of imidazol fragment and amino group at 3100  $\text{cm}^{-1}$ .

In the membrane saturated with arginine the intensity in the region 3600-3000  $\text{cm}^{-1}$  rises and the minima at 3348, 3163, 3058  $\text{cm}^{-1}$  are observed, that characterize the guanidinium fragment vibrations.

The energy of hydrogen bonds ( $E_{\text{H}}$ ) for  $\text{H}^+$ -, arginine and histidine forms of the membranes have been calculated on the basis of the frequency shift value related to the frequency of not-associated OH-group band (3700  $\text{cm}^{-1}$ ) [12]. These data are presented in the Table 2.

Table 2. Parameters of hydrogen bonds for MK-40 and FTCEM-E membranes in  $\text{H}^+$ , arginine and histidine forms

MK-40			FTCEM-E		
Membrane form	$\bar{\nu}_{\text{OH}}, \text{cm}^{-1}$	$E_{\text{H}}, \text{kJ/mol}$	Membrane form	$\bar{\nu}_{\text{OH}}, \text{cm}^{-1}$	$E_{\text{H}}, \text{kJ/mol}$
$\text{H}^+$	3560	9.9	$\text{H}^+$	3496	14.4
	3472	16.1		3413	20.3
	3412	20.4		3301	28.2
	3294	28.7		3074	44.3
	3256	31.4			
	3057	45.5			
	3030	47.4			
Arg	3649	3.6	Arg	3539	11.4
	3618	5.8		3348	24.9
	3562	9.8		3163	38.0
	3398	21.4		3058	45.4
	3285	29.4			
	3059	45.3			
	3038	46.8			
His	3678	1.6	His	3678	1.6
	3447	17.9		3472	16.1
	3258	31.3		3331	26.1
	3203	35.2		3260	31.1
	3032	47.2		3148	39.0

The analysis of hydrogen bonds parameters ( $E_H$ ) leads to the conclusion that water in the phase of cation-exchange membranes saturated in arginine solution forms associates of different structure. In the phase of heterogeneous cation-exchange membrane MK-40 along with the associates  $H_2O \dots SO_3^-$ ,  $H_2O \dots COO^-$ ,  $H_2O \dots H_2O$ ,  $H_2O \dots NH_3^+$  there exist water molecules with distorted, weakened and partially destroyed hydrogen bonds ( $E_H$  is lower than the following value for liquid water).

According to  $E_H$  values for MK-40 and FTCEM-E membrane it is possible to conclude about the presence of water molecules with destroyed hydrogen bonds, of associates water-water in various environment ( $E_H=20.7-26.0$  kJ/mol) and of water molecules participating in hydrogen bonding with sulfo-group ( $E_H > 30$  kJ/mol). For amino acids forms it is evident that energy of hydrogen bonding for water molecules in various states differs substantially. Water molecules with the most strong hydrogen bonding find themselves near the carboxyl-groups of arginine or histidine, intermediate values of  $E_H$  correspond to water molecules participating in the formation of water-water bonds. Molecules of water with destroyed hydrogen bonds are located close to hydrocarbon fragments of amino acid and chains of membrane matrix.

## Conclusion

Thus, analysis of vibrational spectra of heterogeneous membranes (MK-40 and FTCEM-E) confirms earlier drawn conclusions about the different states of water in the phase of membranes with matrix of different chemical nature and structure. In the phase of heterogeneous membrane there exist intergel regions where water structure is the same as in a pure solvent.

To summarize, sorption of arginine and histidine substantially affects the content and state of water in the both membranes. The results obtained can be used to optimize membrane separation, isolation and concentration of basic amino acids.

## References

1. Eliseeva T.V., Krisilova E.V. Recovery of basic amino acids from tartrates solutions with simultaneous concentration by electrodialysis // *Sorbtsion. Khromatogr. Protsessy*. 2008. Vol. 8. Iss.6. P. 1013-1017. [in Russian].
2. Selemenev V.F., Khokhlov V.Yu., Bobreshova O.V. et al. *Physicochemical Bases of Sorption and Membrane Methods of Extraction and Separation of Amino Acids*. Moscow: Stelait. 2002. 298 p. [in Russian].
3. Krisilova E.V., Eliseeva T.V., Selemenev V.F. The hydration of cation-exchange membranes after sorption of basic amino acids // *Zh. Fiz. Khim.* 2009. Vol. 83. № 11. P. 2145-2151.
4. Berezina N.P., Kononenko N.A., Dvorkina G.A. et al. *Fizikokhimicheskie svoistva ionoobmennyykh materialov: praktikum (The Physicochemical Properties of Ion-Exchange Materials: Practical Course)*, Krasnodar: Kuban. Gos. Univ. 1999. 82 p. [in Russian].
5. Roshal E.R., Demina N.G., Sholin A.F. Analysis of amino acids in the form of copper complexes // *Russian Chem.-Pharm. J.* 1988. № 6. P. 30. [in Russian].
6. Rowland S.P., Ed. *Water in Polymers*. ACS Symposium Series 127: Washington. 1980. 532 p.
7. Eliseeva T.V., Shaposhnik V.A., Krisilova E.V., Bukhovets A.E. Transport of basic amino acids through the ion-exchange membranes and their recovery by electrodialysis // *Desalination*. 2009. V. 241. P. 86-90.

8. Krisilova E.V., Eliseeva T.V., Selemenev V.F. Sorption of arginine and lysine by homogeneous cation-exchange membrane MF-4SK // Sorbtsion. Khromatogr. Protsessy. 2009. Vol. 9. № 5. P. 671-676. [in Russian].

9. Bellamy L.J. Infrared Spectra of Complex Molecules. John Wiley & Sons, Inc.: N.Y. 1958. 280 p.

10. Zundel G. Hydrate structures, intermolecular interactions and proton conducting mechanism in polyelectrolyte membranes — infrared results // J. Membr. Sci. 1982. V. 11. Iss. 3. P. 249-274.

11. Zundel G. Hydration Structure and Intermolecular Interaction in Polyelectrolytes // Angewandte Chemie. Int. Edition in English. 1969. V. 8. Iss.7. P. 499-509.

12. Johansen A.V. Infrared Spectroscopy and Spectral Determination of Hydrogen Bond Energy. In: Hydrogen Bond [Russian translation]. Moscow. 1981. P. 112-155.

---

**Lantsuzskaya Elena V.** - Ph.D., Senior Researcher, Department of Analytical Chemistry, Voronezh State University, Voronezh

**Oros Galina Yu.** – Ph. D., Senior Researcher, Department of Analytical Chemistry, Voronezh State University, Voronezh

**Chernikov Mikhail A.** – Postgraduate Student, Department of Analytical Chemistry, Voronezh State University, Voronezh

**Eliseeva Tatiana V.** – Ph.D., Lecturer, Department of Analytical Chemistry, Voronezh State University, Voronezh, [tatyanaeliseeva@yandex.ru](mailto:tatyanaeliseeva@yandex.ru)

**Selemenev Vladimir F.** – Dr. Sc., Prof., Head of Analytical Chemistry Department, Voronezh State University, Voronezh

**Sholokhova Anastasiya Yu.** - student of the Analytical Chemistry department, Voronezh State University, Voronezh